

DOI: <https://doi.org/10.67656/njmse.2020.lasxxxqt>
Nigerian Journal

Of

**Materials Science
and Engineering**

(NJMSE)

Volume 10 Issue 1

ISSN 214-453-2

May 2020

**Materials Science & Technology
Society of Nigeria (MSN)**



An International Journal of the Materials Science and Technology Society of Nigeria

Nigerian Journal of Materials Science and Engineering (NJMSE)

Materials Science & Technology Society of Nigeria (MSN)

Copyright © 2020. Materials Science and Technology Society of Nigeria (MSN)

Volume 10 Issue 1, May 2020
ISSN 214-453-2

All Rights Reserved

Published by

Materials Science and Technology Society of Nigeria (MSN)
National Headquarters
Engineering Materials Development Institute (EMDI)
Km. 4 Ondo Road,
P. M. B. 611, Akure. Nigeria
Tel.: +234-803-471-8487; +234-803-703-3052; +234-806-220-7420

<http://njmse.msn.ng>
NJMSE@msn.ng; njmse.msn@gmail.com; editorinchief@msn.ng; njmsemanagingeditor@msn.ng;
bbabatop@oauife.edu.ng; giwafat2002@yahoo.com

(NJMSE - An International Journal of the Materials Science and Technology Society of Nigeria)

Copyright© 2020. Nigerian Journal of Materials Science and Engineering (NJMSE).

NJMSE Editorial Board

Management Team

Dr. **Babatope** Babaniyi; Obafemi Awolowo University, Ile-Ife. Nigeria. **Editor-in-Chief.**

Prof. **Giwa** Abdulraheem; Ahmadu Bello University, Zaria. Nigeria. **Managing Editor.**

Dr. (Engr.) **Oyelami** Adekunle T., Federal University of Agriculture, Abeokuta, Nigeria.

Assistant Managing Editor

Engr. **Ogunkoya** Olatunji; Engineering Materials Development Institute. Akure. Nigeria.

Editorial Desk / Processing Officer.

Dr. **Edema** O. Gregory, Federal Polytechnic Auchi, Nigeria. **Assistant Processing Officer.**

Associate Editors

Prof. Ishiaku U. S.; Ahmadu Bello University, Zaria. Nigeria

Prof. Tunde Ojumu; Cape Peninsula University of Technology, South Africa.

Prof. Eleruja Marcus Adebola; Obafemi Awolowo University, Ile-Ife. Nigeria

Dr. Umar Ahmadu; Federal University of Technology, Minna. Nigeria

Dr. Ahmed Tajudeen; Federal University Lokoja. Nigeria

Prof. Idenyi Ede Ndubuisi; Ebonyi State University, Abakaliki. Nigeria

Dr. Ajayi Olusegun; Ahmadu Bello University, Zaria. Nigeria

Dr. Adetunji Adelana R.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Baba Alafara; University of Ilorin, Ilorin. Nigeria

Prof. Hassan S. Bolaji; University of Lagos, Lagos. Nigeria

Prof. Nwoye Chukwuka I.; Nnamdi Azikiwe University, Awka. Nigeria

Dr. Oyatogun Grace Modupe; Obafemi Awolowo University, Ile-Ife. Nigeria

Dr. Otemuyiwa I.O; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Ikhuoria Esther; University of Benin. Nigeria

Dr. Oluwajobi Akinjide Olajide, Obafemi Awolowo University. Nigeria.

Dr. Odusanya A. Sola; Sheda Sci. and Technology Complex, Abuja Nigeria

Prof. Borode Joseph Olatunde; Federal University of Technology, Akure. Nigeria

Dr. Odo Dele; Federal University, Oye. Nigeria

Prof. Adewuyi Benjamin; Federal University of Technology, Akure. Nigeria

Dr. Adekunle A. Saheed.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Esezobor David; University of Lagos. Lagos. Nigeria

Prof. Dare E. Olugbenga; Federal University of Agriculture, Abeokuta. Nigeria

Prof. Boyo Adenike; Lagos State University, Lagos. Nigeria.

Prof. Dauda Mohammed; University of Maiduguri, Maiduguri, Nigeria.

Editorial Advisory Board

Prof. Soboyejo Winston 'Wole; Worcester Polytechnic Institute, Worcester. USA

Prof. Salvastano Holmer, Jnr. University of Sao Paulo, Sao Paulo, Brazil

Prof. Thomas Sabu; Mahatma Ghandi University, India

Prof. Sadiku Rotimi; Tshwane University of Technology, Pretoria. South Africa

Prof. Ghosh Malay Kumar; CSIR-IMMT, Bhubanaswar. India

Prof. Olorunnisola Abel Olajide; University of Ibadan, Ibadan. Nigeria

Prof. Ahmed A. Salawu; Ahmadu Bello University, Zaria. Nigeria

Prof. Nkeonye Peter O.; Ahmadu Bello University, Zaria. Nigeria

Prof. Pelemo David A.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Onwualu Peter Azikiwe; University of Nigeria, Nsukka. Nigeria

Engr. Ogundade Kunle; Petroorganico Ltd. Lagos. Nigeria

Prof. Akinola A. P.; Obafemi Awolowo University, Ile-Ife. Nigeria

Editorial Comment

It is a great pressure for the editorial board of the Nigerian Journal of Materials Science and Engineering (NJMSE) to present Volume 10 Number 1 of the journal for 2020 for the world research and development community.

The Materials Science and Technology Society of Nigeria (MSN), as a professional learned body, has made the publication of this research journal to be of very good quality and high standard comparable to any in her class. Our major thrust is to disseminate materials science and engineering and allied research activities from Nigeria, Africa and the world over. We are slowly and gradually impacting on the research community work with this specialised journal from a reputable learned and professional body in Nigeria. We are presently not insisting on number but we very much believe, with the thoroughness of our approach to the review and assessment process, we are convinced that with our resolve to publish quarterly, the board is convinced that more researcher would take advantage of this.

As a journal whose policy is to maintain the standard best practices and in addition to help young researchers to advance in the art and science of scientific findings dissemination, had faced tremendous challenges which were expected. It is heart-warming that we can look back and be glad to see the society publishing the 10th volume. These volumes and the previous ones would be available for FREE downloading on our society website (www.msn.ng) through a link prior to the specialised journal website to be available soon. Arrangements are in advanced stages for the hosting of this journal by reputable international online submission system are being worked on.

Volume 10 (2020) Number 1 consists of eight (8) high standard articles covering different specialised areas of materials research. It is our hope that this humble effort, presently by voluntary efforts of senior members of the Society, at disseminating research findings as put together in this volume which have contributed to the body of knowledge, would have enriched the information base and complemented Materials Research efforts from around the world.

We appreciate all our reviewers and associate editors involved for their prompt action on the manuscripts and cooperation as we look forward to submission of manuscripts which can be forwarded as detailed below.

Babaniyi Babatope. (PhD,MBA,FMSN,FIMMM(UK))
Editor-in-Chief.
Department of Physics and Engineering Physics,
Advanced Nanostructured Materials and Devices Research Group
Obafemi Awolowo University, Ile-Ife. Nigeria.
bbabatop@oauife.edu.ng
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com.

Manuscripts can also be submitted and copied to:

Managing Editors, NJMSE.
njmsemanagingeditor@msn.ng; njmse.msn@gmail.com; njmse@msn.ng.

Editor-in-Chief
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com

Website:
<http://njmse.msn.ng/>

GUIDE TO AUTHORS

AIM: To improve the international exchange of scientific research in materials science and engineering.

INTRODUCTION

The Nigerian Journal of Materials Science and Engineering (NJMSE) publishes reviews, full-length papers, and short communications recording original research results on, or techniques for studying the relationship between structure, properties, and uses of materials. The subjects are seen from international and interdisciplinary perspectives covering areas including metals, ceramics, glasses, polymers, composite materials, fibers, electronic materials, alternative energy materials, nanostructured materials, nanocomposites, biological, biomedical materials, etc. The NJMSE is now firmly established as the leading source of primary communication for scientists investigating the structure and properties of all engineering materials in Nigeria, Africa and the Rest of the World.

UNIQUENESS OF THE JOURNAL

NJMSE is introduced to publish research findings on current topical issues of interest to both public and private sectors. The scope of the Journal focuses on experimental, empirical and theoretical research in Materials Science and Engineering. Findings from multidisciplinary research covering diverse areas of interest with potential impact on the public and private sectors of both the national and international communities will be priorities of the journal. Our major focus is the use of Materials Science and Engineering principles to solve basic problems peculiar to African and the developing world while contributing to knowledge on the global scale.

GUIDE FOR AUTHORS

NJMSE welcomes research papers covering original work that has good potential for practical application. Submission of a manuscript will be held to imply that the work being reported is original and that the result has not been published previously nor been under considerations for publication elsewhere.

MANUSCRIPT PREPARATION

The format of the typescript should be as follows:

The official language of the journal is English. When writing do not mix languages, use US English completely or use UK English completely. It is expected that before submission, the manuscript will have been thoroughly reviewed and written in simple clear expression. Manuscript should be typewritten with double-spacing and 2.54 cm or 1 inch margins on all sides. Manuscripts should be submitted in electronic form and e-mailed directly to the addresses below in MS-Word format, double spacing with graphics at the end. Manuscripts should be arranged in the following order: title page, abstract, introduction, materials and methods, results and discussion, conclusions, acknowledgements, references. The manuscripts should follow the format listed below.

Title: The title page should contain the title [concise but clear expression, written in bold, upper case], followed by the authors [surname first, block letters throughout], and followed by their institutional affiliations and the e-mail address of the corresponding author. In case of many authors, please use numbers to differential their affiliation.

Abstract: An abstract of not more than 350 words should be supplied immediately before the beginning of the paper (Graphical abstracts are also acceptable).

Introduction: This should contain a brief review of literature, clearly stated objectives and justification for the study.

Materials and Methods: This should contain materials preparation procedure and major measurement patterns. Sufficient information should be provided to perform repetition of the experimental work.

Results and Discussion: The result section should contain appropriate tables, figures/illustrations. These should be pertinent to the work and should clearly indicate the degree of reliability of results. Tables should be numbered consecutively, with a short descriptive title in upper case (block letters) on top of the table. They should contain no vertical lines and no lines to separate the rows except the heading and the end of the table. Figures, micrographs, or illustrations must be clearly captioned, the captions at the bottom of each figure. Figures may not be used to repeat the information already presented in tables or text or vice versa. Micrographs and illustrations are considered as figures and must be labeled as such.

Conclusions: These should summarize any important conclusions emerging from the work.

Acknowledgements: These should be presented at the end of text and before the references. Technical assistance and advice may be acknowledged. Acknowledgments of financial support can also be stated in this section.

References:

Citing: Reference in the text should be made by the author's last name and year of publication, e.g. (Abel, 2007); (Abel and Babcock, 2007); (Bowen *et al.*, 2007). Two papers by the same author in the same year should be distinguished by a suffix, (a, b, etc) e.g. (Madonna, 2006a); (Madonna, 2006b).

Listing: This should be in alphabetical order and should follow this format: Name(s) and initial(s) of author(s), (year of publication), exact title of paper (in quote), the title of periodical, Vol. (number): initial and final page numbers. Please note that only name cited in the text can be used.

Serial: Briant C. L. and Banerji S. K. (1981). Tempered Martensite Embrittlement and Intergranular Fracture in an Ultrahigh Strength Sulfur Doped Steel, *Metall. Trans. A*, 12A:309-319. (Please pay attention to punctuations).

Book: Samuels, L.E. (1982). *Metallographic Polishing by Mechanical Methods*, 3ed., American Society for Metals, Metals, Park, Ohio.

Proceeding: Olorunnisola A. O. (2006). The potentials of bamboo as novel building and furniture production materials in Nigeria, pp.180-185. In *Proc. Nigerian Materials Congress (NIMACON 2006)*, (B. Babatope and W.O. Siyanbola, Eds.), organized by Materials Society of Nigeria, 15-18 November 2006, Abuja, Nigeria.

Heading and sub-heading: All headings and sub-headings should be numbered and started from the left hand margin. All headings should be in upper case while sub-headings should be in lower case except the first letter.

Equations: Equations should be distinctly typed using Microsoft equation. Avoid powers of “e” and use “exp”. Equations should be numbered consecutively by Arabic numerals in parenthesis at the right margin. In the text, such equation should be cited as Equation (1) etc.

Units and symbols: Symbols, units and nomenclature should conform to the recommendations of the International Union of Pure Applied Chemistry (IUPAC). SI units should be used for physical quantities.

Peer-Review: All submitted manuscripts are subjected to a peer- review process and galley proofs will be sent to the first or corresponding author where necessary.

SUBMISSION OF MANUSCRIPTS

A Processing Fee of N10,000.00 only is payable per article. All submitted articles MUST be accompanied with scanned Bank (detail below) Tellers or On-line transfer receipt as evidence of payment. Send your article(s) and Bank Teller to: njmse@msn.ng; NJMSE.msn@gmail.com. All submission of manuscripts must be sent on-line to fast-track processing and simplify the refereeing process.

PAGE CHARGE

Corresponding Authors of accepted articles will be required to pay a sum of N10,000.00 only as processing fee (at the point of acknowledging receipt of manuscript) and N10,000.00 (non-members and non-financial members of MSN), N5,000.00 (financial members of MSN) after acceptance (or \$100.00 USD for processing and acceptance for other countries). They will receive free ecopy of the NJMSE volume in .pdf version. The ecopy is available online at <http://njmse.msn.ng> and can be downloaded free. However, printed copy(ies) may be requested for extra payment.

COPYRIGHT

Submission of an article for publication implies the transfer of the copyright of the manuscript from the author(s) to the publisher upon acceptance and that the manuscript has not been previously published elsewhere. This is the responsibility of the authors. Accepted papers become the permanent property of the publisher and may not be reproduced by any means without the written consent of the Editor-in-Chief.

Account Details: GTB PLC A/C No. 0171794514. Materials Science and Technology Society of Nigeria.

All Correspondence to:

Prof. A. Giwa
NJMSE Managing Editor
Department of Polymer and Textile Engineering
Ahmadu Bello University
Zaria, Nigeria. +2348037033052; +2348025672474
giwafat2002@yahoo.com.

Engr. Adetunji Ogunkoya
NJMSE Desk /Processing Officer,
Engineering Materials Development Institute (EMDI)
Ondo Road, PMB 611,
Akure Nigeria. +2348062207420; +2347081019516

<http://njmse.msn.ng/>

Emails: njmse@msn.ng; njmse.msn@gmail.com; njmsemanagingeditor@msn.ng;
editorinchief@msn.ng; njmse.editor.in.Chief@gmail.com;

TABLE OF CONTENT

Olugbade Emmanuel, Zhou Bin, Ikeagwuonu Clement, Yang Li, and Huang Gen-Zhe Microstructure and Hardness Profiles of Hybrid Laser-Arc Welded Joint for Ultrahigh-Strength Steel	1 - 9
Kareem Aduagba Ganiyu; Abdulrahman Asipita Salawu; Abdulkareem Ambali Saka and Tijani Jimoh Oladejo Optimization of the Green Synthesis of Tin Oxide Nanoparticles by Response Surface Methodology (RSM) using Box-Behnken Design	10 - 17
Adewumi Olusegun Emmanuel, Taleatu Bidini Alade, Adewinbi Saheed Adekunle, Busari , Rafiu Adewale, Oyedotun Kabir Oyeniran and Omotoso Ezekiel Synthesis and Surface Characterisation of Cu-Doped Tin Oxide Thin Film for Optoelectronic Applications	18 - 23
Oyegbami Victoria Bola,, Odebunmi Ezekiel Oluyemi, ¹ Odeyemi Omolola Titilayo and Gbadamosi Mustapha Tunde Comparative Activity of Undoped TiO ₂ and 5% N-TiO ₂ for Photocatalytic Degradation of Indigo Carmine Dye	24 - 29
Olofinjana Bolutife, Ajayi Oyelayo, Lorenzo-Martin Cinta, Ajayi Ezekiel Oladele Bolarinwa Effect of Counterface Material on Tribological Behavior of AISI 304L Stainless Steel Under Marginally Lubricated Contact	30 - 36
Maliki Muniratu, Inobeme Abel, Kelani Tawakalit Omolara and Eziukwu Chinenye A. Physicochemical and Heavy Metals Analysis of Water from Different Sources in Usen, Edo State, Nigeria.	37 - 41
Muazu Alhassan, Ahmadu Umaru, Auwalu Inusa A., Zangina Tasiu, Nura Abdullahi and Maharaz M. Nasir Impedance and Modulus Spectroscopy of Nanocrystallite Barium Titanate Ceramic Using Mechanochemical Method.	42 - 50

Synthesis and Surface Characterisation of Cu-Doped Tin Oxide Thin Film for Optoelectronic Applications

Adewumi Olusegun Emmanuel, Taleatu Bidini Alade, ¹Adewinbi Saheed Adekunle, ²Busari, Rafiu Adewale, ³Oyedotun Kabir Oyeniran and *Omotoso Ezekiel

Department of Physics and Engineering Physics, Obafemi Awolowo University, Ile-Ife, Nigeria

¹Department of Physics, Osun State University, Osogbo, Osun State, Nigeria

²Centre for Energy Research and Development, Obafemi Awolowo University, Ile-Ife, Nigeria

³Department of Physics, Institute of Applied Materials, Carbon Technology and Materials, University of Pretoria, Pretoria 0002, South Africa

*Corresponding Author's e-mail: omotoeze@gmail.com

Abstract

Copper doped tin oxide thin film was synthesised by electrodeposition technique. Film growth was maintained at cathodic potential of 1.60 V at a varied deposition time. Surface morphological studies of the deposited films were achieved by field emission scanning electron microscopy (FE-SEM). The scanning electron microscopy image revealed evenly distributed films, across the substrate with rice-like or dome-like particles, depending on the deposition time. Post-annealing enhanced films crystallinity and particles agglomeration. Energy disperse X-ray spectra revealed the elemental constituents present in the film. The results obtained from electrical characterisation of the samples showed the ohmic properties of the deposited sample. X-ray diffraction results indicated that samples are polycrystalline in nature with tetragonal rutile structure. The average interplanar spacing and crystallite size of the samples were estimated as 2.93 Å and 202.5 Å respectively. Optical characterisation of the samples showed that absorption and transmittance across the ultraviolet-visible spectrum range depend on deposition time. The estimated energy band gaps of 3.06 eV suggested the films as good candidates for transparent contact electrodes in optoelectronic applications.

Keywords: Electrodeposition, Annealing, Doping, Crystallinity, Morphology, Energy band gap

INTRODUCTION

It has been noted that nothing compares with the sun energy potential. Solar power is readily abundant and efficient to supply the world's energy needs. Since solar energy can be sustained and renewed, its availability cannot be exhausted (Görig and Breyer 2016). Global warming is characterised by disastrous effects, consequently threatening its detrimental influence on climate, environment (with plants and animals) and human health (Resch *et al.* 2008). Significant source of greenhouse gases (GHG) are power plants (coal-fired).

These are accountable for about 25% of all anthropogenic emissions (Kabir *et al.* 2018), however, the emission of these gases during production of solar power is insignificant. The ratio of CO₂ emitted per KWh obtained from solar power, natural gas and coal are estimated to be 1:9.5:18 respectively (Machol and Rizk, 2013). This corroborates how friendly solar energy is to the environment when compared to other sources of energy (Weisser 2007). Solar power has a realistic solution to lessen global warming crisis, it can effectively replace coal and gas-based energy sources creating an environment with social and economic benefits for attaining sustainable development. Solar energy is a consistent, clean and pollution free source of energy. Distinct from other energy sources, its consumption is not accompanied by the release of injurious gases (e.g. volatile organic compounds (VOCs)) or oxides of carbon, nitrogen and sulphur (CNS) and particles (e.g. metals, soot carbon black, particulate matter (PM) and so on). It has thus been

reported that replacing fossil fuels with renewable energy could lessen untimely death rates, lost workdays, and moderate the costs for healthcare delivery (Weisser 2007; Patterson *et al.* 2016). By 2050, growth in world renewable energy consumption is anticipated to increase from 13 terawatts per year to about 30 terawatts (Kabir *et al.* 2018). In this regard, photovoltaic systems are potential devices that can convert solar energy and contribute significantly to the world energy since 100 PW irradiated power hits the earth surface on a sunny day (Luque and Hegedus 2011).

In transparent conducting oxides, combination of high optical transparency in the visible region of e-m spectrum and high electrical conductivity are qualities not easily achieved. A band gap greater than 3.2 eV is required for optical transparency in order to prevent absorption of electromagnetic spectrum in the visible region. Doping of metal oxides become very difficult as a result of this (Hosono 2007). For instance, if a suitable band gap in the host material electronic band structure and an appropriate donor energy level for an n-type dopant species are designed for a host material band structure, the ability of the host material to receive such dopant must be taken into consideration (Xu and Schoonen 2000). By this assertion, an increase in the deposition time of copper doped tin oxide leads to increase in the density of states generated by the impurities and forms a continuum of states below the conduction band leading to narrowing of the band gap of the host oxide. As a result, Cu-SnO₂ thin film has been observed in this study as a candidate for transparent

contact electrode material in the fabrication of optoelectronic and energy storage devices.

EXPERIMENTAL PROCEDURE

Two different samples of Cu-SnO₂ were prepared at different deposition time. The substrate used for this work is Indium Tin Oxide (ITO) coated glass of 20 mm × 15 mm × 0.7 mm dimension. A simple home-made two electrode cell was used for the growth of the films. The advantages of the home-made electrode cell include low cost, high purity product, low temperature growth and ease of tunability for desired stoichiometry by a simple adjustment of deposition factors (Chopra *et al.* 2004).

Preparation of precursor and sample deposition

A solution precursor (electrolyte) was prepared from some common chemical reagents. 5.64 g of SnCl₂·2H₂O salt was dissolved in 250 ml of distilled water to form 0.1 M of SnCl₂ solution. KOH of 0.1 M was prepared by dissolving 1.40 g of potassium hydroxide pellet in 250 ml of distilled water. Also, Cu(NO₃)₂ of 0.01 M was obtained by dissolving 0.24 g of Cu(NO₃)₂·5H₂O in 100 ml of distilled water. All the solutions prepared were kept in different standard flasks at room temperature (300 K) for twenty-four hours for a complete dissolution. Before sample deposition, some ITO coated glasses were washed properly with detergent, which were subsequently cleaned in an ultrasonic bath that contained acetone and methanol separately. The substrates were later dried briefly in an oven at a temperature of 110°C. For the deposition of Cu-SnO₂ thin film, an electrolytic solution containing 20 ml of 0.1 M of SnCl₂, 20 ml of 0.1 M of KOH and 5 ml of 0.01 M of Cu(NO₃)₂ was poured into the electrolytic container. The counter electrode (graphite) and the working electrode (ITO substrate) were held firmly to the holders and connected to power source and digital multimeter to achieve stabilized power. A cathodic potential of 1.60 V was selected for running the experiment in potentiostatic mode with anodic current degrading with growth time. Two samples tagged A1 and A2 were obtained at growth periods of 10 and 20 minutes, respectively.

Sample characterisation

After drying the deposited films at 120°C for 5 minutes, they were annealed at 350°C in air for 1 hour. Surface morphology and chemical composition were studied using Zeiss ultra plus field emission scanning electron microscopy (FE-SEM) attached with energy dispersive X-ray spectroscopy (EDX) facility. An XPERT-PRO X-ray diffractometer (PANalytical BV, Netherlands) with reflection geometry ranging from 2θ values of 10 to 90° and having a step size of 0.01° and also operating with a Co Kα radiation source (λ = 0.178901 nm) at 50 kV and 30 mA was used to obtain the X-ray diffraction patterns. Optical absorption as well as transmittance of deposited films were studied across the visible spectrum region by a double beam UV/VIS spectrophotometer. Electrical characterisation of deposited thin films was investigated

by a sheet resistance four probe station (T2001A1).

RESULTS AND DISCUSSION

Crystal structures and orientation

Figure 1 depicts the XRD pattern of Cu-SnO₂ thin film. Reflections along (220), (101), (200), (211) and (310) planes correspond to single phase of tetragonal rutile structure. Other observable peaks are attributed to ITO coated glass substrate (Jiang *et al.* 2008). Peak at the (101) plane is the most prominent, and it signifies a preferential growth orientation of the film particles. It was also observed that the intensity of the dominant peak (101) decreases with increase in deposition time. This suggests a slight deterioration in the crystallinity of SnO₂ structure, which could be attributed to the stress (contraction in the lattice due to copper [Cu²⁺: 0.73 Å] substituting some tin [Sn⁴⁺: 0.83 Å] sites) (Bagheri-Mohagheghi and Shokooh-Saremi 2004).

Across all the diffraction angles, several peaks due to Cu²⁺ ions were not detected, this is probably due to a low percentage of the dopant, which agrees with some findings in literatures. It could even be due to some limitations from the XRD machine used especially its power ratings which may not be sufficient enough to identify the Cu particle (Choudhury *et al.* 2015; Benzitouni *et al.* 2016). The reference card number for

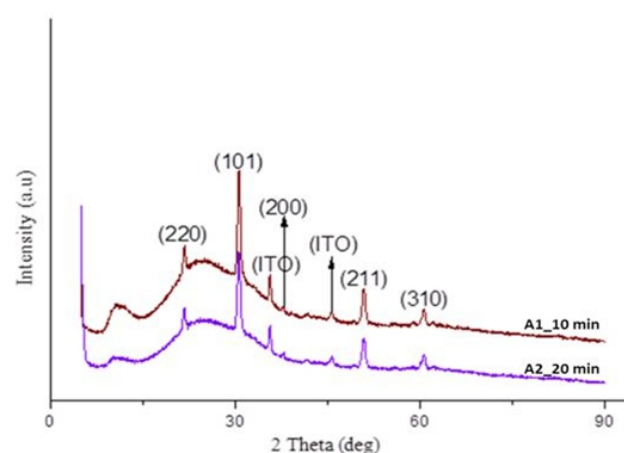


Figure 1: XRD patterns of Cu-SnO₂ thin films at different deposition times.

the diffraction pattern obtained is with respect to JCPDS card number: 41-1445. Interplanar spacing, *d*, of the deposited thin film was determined by Equation.(1).

$$\frac{1}{d^2} = \frac{h^2 + k^2}{a^2} + \frac{l^2}{c^2} \quad (1)$$

where *a* and *c* are lattice constants, and *h*, *k*, *l* are Miller indices. Williamson Hall's modified Debye Scherrer's formula in Equation 2 was used to determine the crystallites size of Cu-SnO₂ thin film (Gultekin *et al.* 2012):

$$\beta = \frac{k\lambda}{D\cos\theta} + 4\epsilon\tan\theta \quad (2)$$

where the constant κ is 0.94, λ is the wavelength of the incident X-ray, β is the full width at half maximum (FWHM) of the most prominent peaks, measured in radians and θ is Bragg's diffraction angle and ϵ is the residual lattice strain of the thin films. The intercept and slope of the plot of $\beta \cos \theta$ versus $\sin \theta$ were used to deduce the average crystal sizes and lattice strains of the samples respectively (Bagheri *et al.* 2013).

Dislocation density, δ , was determined using the Equation (3) (Cullity and Stock 1956):

$$\delta = 1/d^2 \quad (3)$$

where d is the interplanar spacing.

Table 1 lists the value ϵ , D , δ , a , b and FWHM of the materials. From the table, it can be observed that the interplanar spacing d , crystallite size D , dislocation density δ and lattice strain ϵ of the material increased with increase in the dopant concentration. The increase in these properties shows that the increase in concentration of impurities can influence the crystal properties of electrodeposited nanostructures.

Surface morphology

Figure 2 (a and b) shows the SEM micrographs of Cu-SnO₂ thin films. The particles are evenly distributed across the substrate, some of these particles are isolated, and some drift to form an agglomeration of particles exhibiting polycrystallinity. A distinct rice-like structure is observed on sample A1, such structure can allow easy passage of photons to proximate layer in photovoltaic device architecture. As the deposition time increases, less distinct but bigger dome-like

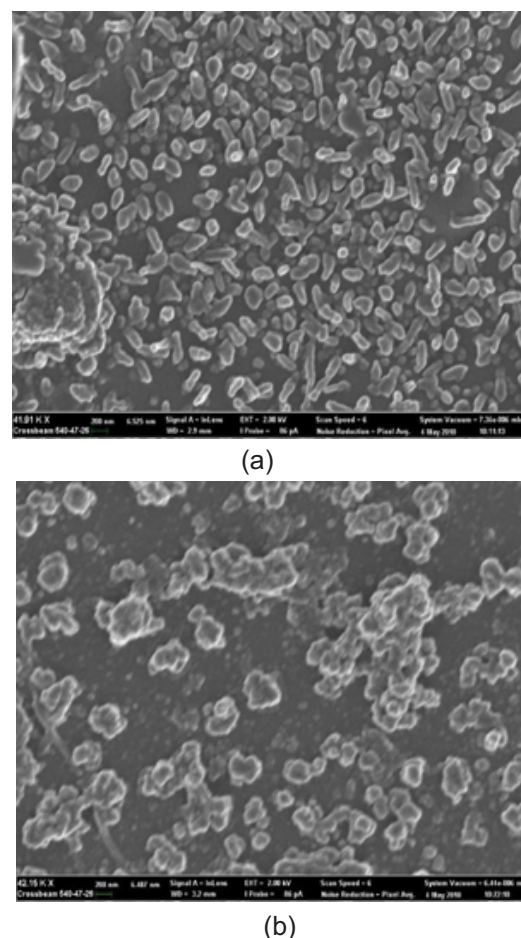


Figure 2: Surface morphology of the Cu-SnO₂ thin films at different deposition time for (a) A1 at 10 min and (b) A2 at 20 min.

Table 1: Calculated data from XRD pattern with a and b as lattice constants

Sample	2	hkl	FWHM	Lattice Constant		d (Å)	D (nm)	$(nm)^2$	ϵ
				a	b				
A1	30.68	101	0.3486	4.821	3.352	2.91	18.89	5.87	0.169
A2	30.45	101	0.5821	4.813	3.341	2.95	21.61	16.40	0.277

particles with apparent surface defects that could be traced to stress emerged. Also, the image analyses revealed the particle size of sample A1 in nanometer scale (~15 nm) but at higher deposition time, the nanoparticles agglomerated to form cluster of particles and therefore enhanced particle sizes in samples A2 (~28 nm). In addition, the post-deposition annealing improves the crystallinity of the deposited layer. The absence of cracks in all the images could suggest that Cu ions (dopant) are well incorporated in the lattice of the host material (Zhang *et al.* 2013).

Films Composition

The deposited samples were quantitatively analyzed by Energy Dispersive Spectroscopy (EDS). The spectra obtained is shown in Figure 3. The spectra reveal the presence of Sn and O along with some quantities of

copper. Other spectra observed are due to other elements present in the substrate and impurity atoms. The percentage atomic weight of the grown Cu-Sn-O and other elements due to the substrate are presented in Table 2.

Electrical Characterisation

The electrical characterisation of deposited thin films was investigated by sheet resistant probe station (T2001A1). The result of the current-voltage measurement obtained for ITO and the deposited samples are presented in Figure 4(a-c). The plots revealed that the samples are ohmic conductor. The resistivity, conductivity and sheet resistance of ITO, and samples at different deposition time were determined by Equations (4) to (6).

$$\rho = R_s t_p \quad (4)$$

where ρ is the resistivity, R_s is the sheet resistance and t_p

$$\sigma = 1/\rho \quad (5)$$

where σ is the conductivity and ρ is the resistivity.

$$R_s = 4.53V/I \quad (6)$$

R_s is the sheet resistance, the applied inner voltage is denoted by V , and I the outer current. The results from the above equations are presented in Table 3. From the results, it is observed that sample A2 with higher deposition time has higher conductivity and lower sheet resistance than sample A1. This suggests its suitability as a transparent contact electrode for optoelectronic applications.

Optical characterisation

Optical properties of the films were studied across UV/VIS range. The transmittance and absorption coefficient curves are presented in Figure 5. All the samples exhibited high absorbance in ultraviolet region. Absorbance drops from visible to infrared region with an occurrence of red shift in spectra presented in Figure 5a. Sample deposited at longer time absorbs better, this could be as a result of the thickness of the film. Absorption coefficient varies with photon energy at the optical absorption edge, this is due to electron excitation to higher energy level. Some metal oxides with such absorption band are used in organic

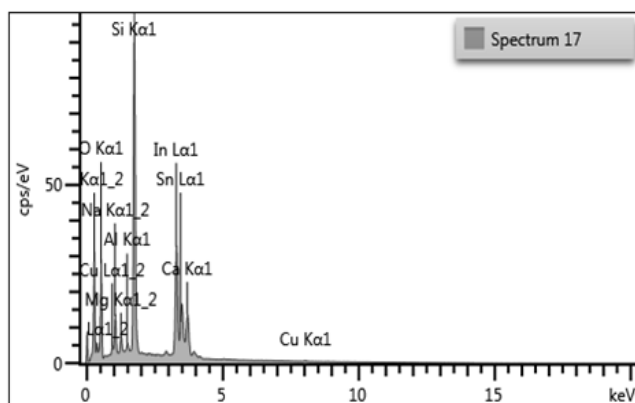


Figure 3: EDX elemental analysis of deposited Cu-SnO₂ thin film.

Table 2: EDX elemental analysis of electro-deposited Cu-SnO₂ thin film

Element	wt%	Atomic %
O	23.17	48.11
Na	3.68	5.32
Mg	1.22	1.67
Al	0.57	0.71
Si	23.44	27.73
Ca	4.11	3.41
Cu	1.81	0.95
In	37.08	10.73
Sn	4.92	1.38
Total	100.00	100.00

Table 3: Electrical measurement of blank indium tin oxide (ITO) and Electrodeposited Cu-SnO₂ Samples

S/N	Sample	Conductivity (Ωm) ⁻¹	Resistivity (Ωm)	R _{Sheet} (Ω)
1	ITO	7.869×10^5	1.26×10^{-6}	12.70
2	A1	9.427×10^5	1.06×10^{-6}	1060.79
3	A2	1.438×10^5	6.95×10^{-6}	69.53

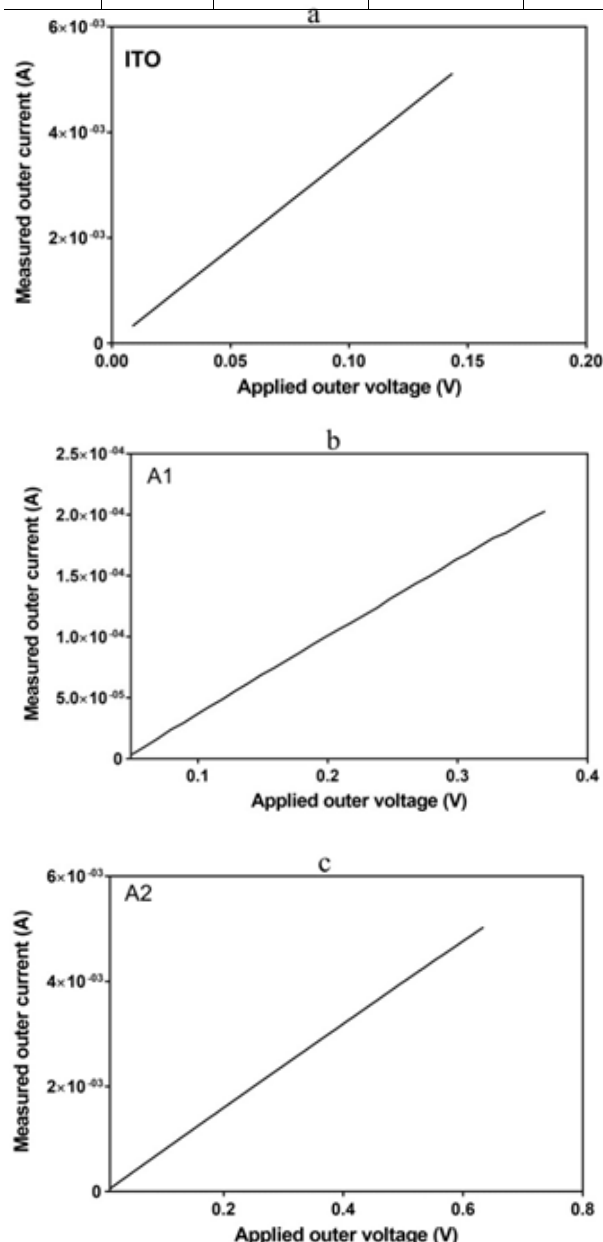


Figure 4: Plots of ITO and the Cu-SnO₂ thin film deposited at different deposition time (a) ITO (b) 10 min (c) 20 min.

photovoltaic cell as buffer layer (Benhaliliba *et al.* 2011). This implies that the deposited Cu-SnO₂ films can be used to make contact electrode capable of selectively absorbing photons across wide wavelength region and at the same time minimize recombination of photogenerated excitons. In Figure 5b, the Cu-SnO₂ samples obtained at shorter time exhibits better

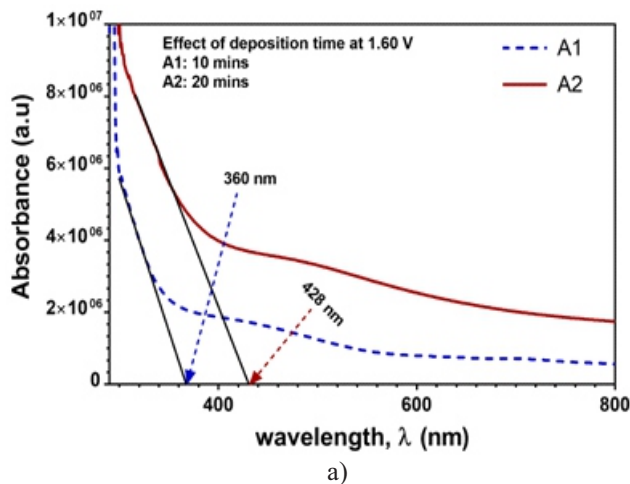


Figure 5a: UV-Visible absorption coefficient spectrum of deposited Cu-SnO₂ thin film. The absorption edges for A1 and A2 are 360 and 428 nm, respectively.

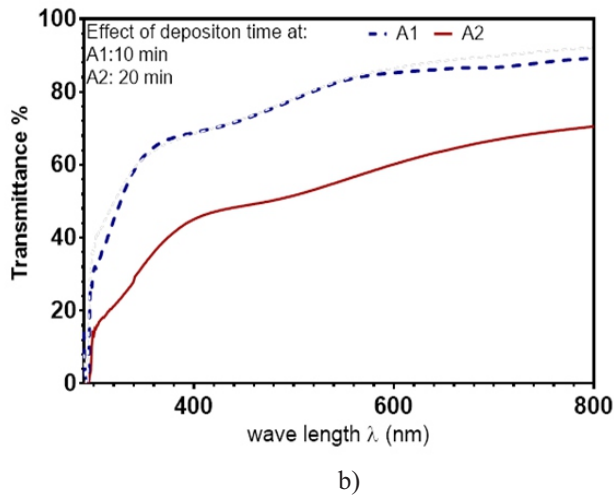


Figure 5b: UV-Visible transmittance spectrum of deposited Cu-SnO₂ thin film

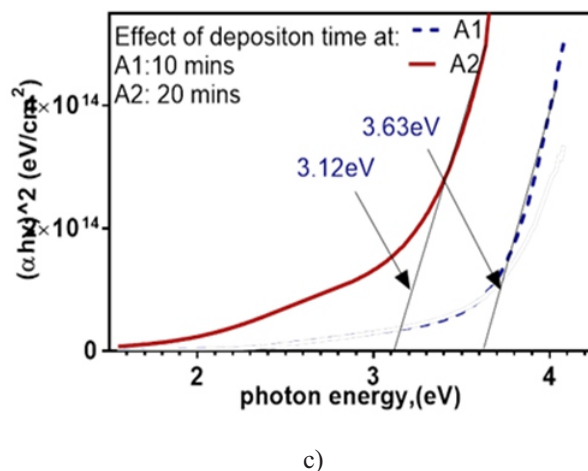


Figure 5c: Tauc's plot for the estimation of energy band gap of Cu-SnO₂ thin film. The energy band gaps are A1 = 3.63 eV and A2 = 3.12 eV.

transmittance in the visible region. The absorption coefficient (α) could be calculated by the relation below (Guascito *et al.* 2008):

$$\alpha = 2.303 A/t \quad (8)$$

where A is the absorbance and t is the film thickness.

Tauc's plots in Figure 5c were generated from the measured absorption data. The energy band gaps were estimated in Equation. 9.

$$\alpha h\nu = B(h\nu - E_g)^n \quad (9)$$

where direct and indirect band gap are denoted by $n = 1$ and 4 respectively. α is the absorption coefficient (Anthony *et al.* 2007; Pradhan and Leung 2008), B is an empirical constant, $h\nu$ is the photon energy and E_g represents the energy band gap. The energy band gaps of the samples were estimated by extrapolating the linear portion of $(\alpha h\nu)^2$ values plotted against $h\nu$ axis at $(\alpha h\nu)^2 = 0$ (Jones and Lettington 1972; Márquezet *et al.* 1992). It was observed that the optical band gap decreased with longer deposition time. Spectrum obtained from sample A2 deposited at longer deposition time manifested lower optical band gap compared to that of A1 obtained at shorter times. This could be attributed to the thickness of the film. This lower energy band gap is specifically due to the addition of donor energy level by impurities, into the band gap of SnO₂, which shifts Fermi level closer to the band edges (Xu and Schoonen 2000).

With increase in the deposition time of copper doped tin oxide, the density of states generated by impurities increased and formed a continuum of states below the conduction bands leading to reduction in band gap. Consequently, there can be higher charge mobility and reduced rate of surface recombination.

Figure 5c presents a plot of skin depth against photon energy. It can be observed from the plot that the skin depth decreased with photon energy. The spectra also revealed that sample A1 demonstrated higher skin depth than sample A2. The behaviour of the spectra revealed that skin depth was transmittance-related.

CONCLUSION

In this study, Cu-SnO₂ thin film was deposited successfully on ITO coated glass using the electrodeposition technique. XRD pattern of the film was characterised with multiple peaks implying that the film is polycrystalline, with tetragonal structure. Morphological studies revealed compact, uniform and well distributed films, across the surface of the substrate. Polycrystals are formed by grain agglomeration and post-deposition annealing improved film crystallinity. EDX spectra revealed peaks that correspond to elements and compositions of the films and substrates. Other peaks are attributed to impurities. The deposited samples revealed ohmic properties by electrical characterisation. The optical absorption edges were determined between 360 and 428 nm for the samples respectively. Estimated direct energy gaps were 3.12 and 3.63 eV for the samples A1 and A2. This suggested that the deposited films can function efficiently as a

transparent contact electrode in optoelectronic devices.

ACKNOWLEDGMENT

This work is based on research supported by The World Academy of Science and the Abdus Salam International Centre for Theoretical Physics with Grant number 15-049 RG/PHYS/AF/AC_I-FR3240287081. The authors thanked M.A. Rahman of the Chemistry laboratory, Department of Chemistry, Obafemi Awolowo University, Ile-Ife, Nigeria. Contributions to this work by members of staff of Materials Science laboratory in the Department of Physics and Engineering Physics are also acknowledged. The Carbon-Technology laboratory group of the Department of Physics, University of Pretoria is also acknowledged for their assistance on SEM and XRD characterisation.

REFERENCES

- Anthony, S. P., Lee, J. I., and Kim, J. K. (2007). "Tuning optical band gap of vertically aligned ZnO nanowire arrays grown by homoepitaxial electrodeposition". *Appl. Phys. Lett.*, 90(10): 103107.
- Bagheri, S., Chandrappa, K. G., and Hamid, S. A. (2013). "Facile synthesis of nano-sized ZnO by direct precipitation method". *Der Pharma Chemica*, 5(3): 265-270.
- Bagheri-Mohagheghi, M. M., and Shokooh-Saremi, M. (2004). "The influence of Al doping on the electrical, optical and structural properties of SnO₂ transparent conducting films deposited by the spray pyrolysis technique". *J. Phys. D: Appl. Phys.*, 37(8): 1248.
- Benhaliliba, M., Benouis, C. E., Boubaker, K., Amlouk, M., and Amlouk, A. (2011). "A new guide to thermally optimised doped oxides monolayer spray-grown solar cells: the Amlouk-Boubaker optothermal expansivity. In *Solar Cells-New Aspects and Solutions*". *Intech Open*: 112-133
- Benzitouni, S., Zaabat, M., Khial, A., Rechem, D., Benaboud, A., Bouras, D., and Coste, R. (2016). "High sensitivity of porous Cu-doped SnO₂ thin films to methanol". *Adv. Nanoparticles*, 5(2): 140.
- Chopra, K. L., Paulson, P. D., and Dutta, V. (2004). "Thin film solar cells: an overview". *Prog. Photovoltaics Res. Appl.*, 12(2-3): 69-92.
- Choudhury, B., Choudhury, A., and Borah, D. (2015). "Interplay of dopants and defects in making Cu doped TiO₂ nanoparticle a ferromagnetic semiconductor". *J. Alloys and Compd*, 646: 692-698.
- Cullity, B.D and Stock S.R (1956). The direction of diffracted beam. *Elements of X-ray diffraction*, Addison-Wesley Publishing Co., USA: 78-103
- Görig, M., and Breyer, C. (2016). "Energy learning curves of PV systems". *Environ. Prog. Sust. Energy*, 35(3): 914-923.
- Guascito, M. R., Filippo, E., Malitesta, C., Manno, D., Serra, A., and Turco, A. (2008). "A new amperometric nanostructured sensor for the analytical determination of hydrogen peroxide". *Biosens. Bioelectr.*, 24(4): 1057-1063.
- Gultekin, D., Alaf, M., Guler, M. O., and Akbulut, H. (2012). "Synthesis of ZnO, SnO₂ Nanoparticles and Preparation of ZnO-SnO₂ Nanocomposites". *J. Nanosci. Nanotechnol.*, 12(12): 9175-9182.
- Hosono, H. (2007). "Recent progress in transparent oxide semiconductors: Materials and device application". *Thin Solid Films*, 515(15): 6000-6014.
- Jiang, D. Y., Shen, D. Z., Liu, K. W., Shan, C. X., Zhao, Y. M., Yang, T. and Zhang, J. Y. (2008). "Effect of post annealing on the band gap of Mg_xZn_{1-x}O thin films". *Semiconduct. Sci. Technol.*, 23(3): 035002.
- Jones, D., and Lettington, A. H. (1972). "The electronic band structures of the wide band gap semiconductors GaN and AlN". *Solid State Comm.*, 11(5): 701-705.
- Kabir, E., Kumar, P., Kumar, S., Adelodun, A. A., & Kim, K. H. (2018). "Solar energy: Potential and future prospects". *Ren. Sust. Energy Reviews*, 8(2): 894-900.
- Luque, A., and Hegedus, S. (2011). "Handbook of Photovoltaic Science and Engineering". John Wiley & Sons, New Jersey, USA: 332-328
- Machol, B., and Rizk, S. (2013). "Economic value of US fossil fuel electricity health impacts". *Environ. Int.*, 5(2): 75-80.
- MÁrquez, E., Ramirez-Malo, J., Villares, P., Jimenez-Garay, R., Ewen, P. J. S., and Owen, A. E. (1992). "Calculation of the thickness and optical constants of amorphous arsenic sulphide films from their transmission spectra". *J. Phys. D: Appl Phys.*, 25(3): 535.
- Patterson, T. F., Thompson III, G. R., Denning, D. W., Fishman, J. A., Hadley, S., Herbrecht, R. and Segal, B. H. (2016). "Practice guidelines for the diagnosis and management of aspergillosis: 2016 update by the Infectious Diseases Society of America". *Clinical Infectious Diseases*, 63(4): 1-60.
- Pradhan, D. and Leung, K. T. (2008). "Controlled growth of two-dimensional and one-dimensional ZnO nanostructures on Indium Tin Oxide coated glass by direct electrodeposition". *Langmuir*, 24(17): 9707-9716.
- Resch, G., Held, A., Faber, T., Panzer, C., Toro, F., and Haas, R. (2008). "Potentials and prospects for renewable energies at global scale". *Energy policy*, 36(11): 4048-4056.
- Weisser, D. (2007). "A guide to life-cycle greenhouse gas (GHG) emissions from electric supply technologies". *Energy*, 32(9): 1543-1559.
- Xu, Y., and Schoonen, M. A. (2000). "The absolute energy positions of conduction and valence bands of selected semiconducting minerals". *Am. Mineralogist*, 85(3-4): 543-556.
- Zhang, S., Li, W., Yao, L., Pan, Y., Shen, F., Xiao, R. and Ma, Y. (2013). "Enhanced proportion of radiative excitons in non-doped electro-fluorescence generated from an imidazole derivative with an orthogonal donor-acceptor structure". *Chem. Comm.*, 49(96): 11302-11304.